

# OPTIMIZATION OF MACHINING PARAMETERS FOR THE ROUGHING OPERATION OF ASTM A744 STEEL

## OTIMIZAÇÃO DE PARÂMETROS DE USINAGEM PARA A OPERAÇÃO DE DESBASTE DE UM AÇO ASTM A744

Márcio Tadeu Gravalos<sup>1</sup>, Marcelo Martins<sup>1</sup>, Anselmo Eduardo Diniz<sup>2</sup> & Paulo Roberto Mei<sup>2</sup>

<sup>1</sup> Sulzer Brasil S/A, [marcio.gravalos@sulzer.com](mailto:marcio.gravalos@sulzer.com)

<sup>2</sup> Faculdade de Engenharia Mecânica da Unicamp, [pmei@fem.unicamp.br](mailto:pmei@fem.unicamp.br)

### Abstract

An investigation was made into the effects of the machining conditions of the turning operation on the surface integrity of ASTM A744 Grade CN3MN superaustenitic stainless steel. The main focus was the roughing operation. The input variables were cutting depth of 2.5 mm, feed rate of 0.25 mm/rot., rake angle (0 or 10°) and cutting speed (60 or 90 m/min). The tests were conducted on a CNC horizontal lathe, using a flood of cutting fluid. The following parameters were analyzed: microstructure and roughness – examined by optical microscopy; work hardening – determined by microhardness measurements; and residual stress – analyzed by X-ray diffraction. The results revealed the presence of residual tensile stress and a hardened layer on all the machined surfaces. To obtain the lowest values of roughness and residual tensile stress at a cutting depth of 2.5 mm and a feed rate of 0.25 mm/rot., the best combination was the lowest cutting speed (60 m/min) and the highest rake angle (10°).

**Keywords:** Superaustenitic stainless steel, machining, roughness, residual stress.

### Resumo

*Foram investigados os efeitos das condições de usinagem em operação de torneamento na integridade superficial do aço inoxidável superaustenítico ASTM A744 Gr.CN3MN. A operação de desbaste foi o foco principal. As variáveis de entrada foram a profundidade de corte de 2,5 mm, o avanço de 0,25 mm/rot., o ângulo de saída da ferramenta (0 ou 10°) e a velocidade de corte (60 ou 90 m/min.). Os ensaios foram realizados em um torno horizontal CNC, utilizando fluido de corte. Os parâmetros analisados foram: microestrutura e rugosidade - por microscopia ótica, encruamento - por ensaio de microdureza e tensão residual - por difração de raio-X. Os resultados mostraram a presença de tensão residual de tração e de uma camada encruada em todas as superfícies usinadas. Para obter os menores valores de rugosidade e de tensão residual de tração, para a profundidade de corte de 2,5 mm e avanço de 0,25 mm/rot., a melhor combinação das condições de corte encontrada foi a menor velocidade de corte (60 m/min) e o maior ângulo de saída (10°).*

**Palavras-chave:** Aço inoxidável superaustenítico, usinagem, rugosidade e tensão residual.

## 1 – Introduction

Superaustenitic stainless steel is composed of a predominantly austenitic structure. Its high nickel and molybdenum content and the presence of nitrogen give superaustenitic steel higher corrosion resistance than series 300 conventional austenitic stainless steel (Curtis et al., 2002). Due to their high pitting corrosion resistance, superaustenitic alloys are one of the materials used in the manufacture of components for pumps operating in maritime environments.

Machining is one of the most important processes involved in the fabrication of pump components. When an as-machined surface is in service, its quality may impair its resistance to pitting corrosion and stress corrosion (Braman et al., 2005; Rhouma et al., 2001). Surface integrity is the quality of machined surfaces interpreted as a function of the elements that describe the structure of the surface and the material. This integrity is usually defined by the material's metallurgical and chemical properties, its hardness, roughness, microstructure and residual stress (Jang et al., 1996; Matsumoto et al., 1986) (Jang et al., 1996; Matsumoto et al., 1986). The pitting corrosion resistance of a machined surface increases as the degree of surface finishing decreases (Hassiotis et al., 2006; Moyaed et al., 2003; Salina-Bravo et al., 1994; Ramanathan, 1998), while its resistance to stress corrosion increases as the residual stress introduced during machining decreases (Braman et al., 2005).

Turning is a machining process most widely used of all industrial machining processes (Shaw, 2005), representing 70% of the total number of hours spent in machining pump components. Turning is also one of the most common processes in experimental research on metal cutting (Trent et al., 2000). The turning conditions applied influence the quality of a machined surface (Diniz et al., 2003).

Not all the surfaces of cast rotary components used in pumps require good finishing and low roughness, especially when such surfaces do not require tight dimensional and geometric tolerances. Therefore, it is important to study the effects of machining on the quality of a rough-turned surface.

Since the characteristics and properties of superaustenitic stainless steel differ from those of conventional austenitic stainless steel, there is a clear need to study the machining of these steels. The objective of this work is to investigate the effect of the cutting conditions employed in the rough turning operation on the surface quality of samples of casting alloy of ASTM A743 CN3MN (1998) superaustenitic stainless steel based on an analysis of the influence of surface roughness, surface hardening and residual stress.

## 2 – Materials and methods

The CN3MN superaustenitic stainless steel samples used in this study were cylindrical, with a 95 mm diameter and 200 mm length, cast by the static process and solution heat-treated at 1170°C for 2 hours.

Hardness was measured with a Buehler 1600-6300 microhardness tester, applying a load of 50 gf for 10 seconds. The measurements were taken from the machined surface toward the core, at intervals of 50 µm. The hardness measured in the region of the core, which did not undergo machining, was in the order of  $226 \pm 7$  HV.

Table 01 shows the chemical composition and PRE<sub>N</sub> (*Pitting Resistance Equivalent*) values calculated by the equation:  $PRE_N = Cr\% + 3.3Mo\% + 16N\%$ .

Table 01 – Values of chemical compositions (% weight) and PRE<sub>N</sub>

Element	Si	C	Mo	Cr	Si	Ni	P	Mn	Cu	N	PRE <sub>N</sub>
Sample	0.74	0.015	6.25	20.79	0.008	24.65	0.021	0.63	0.33	0.2	44.6
Standard	1 Max.	0.03 Max.	6.0 a 7.0	20 a 22	0.01 Max.	23.5 a 25.5	0.04 Max.	2 Max.	0.75 Max.	0.18 a 0.26	≥ 40

The cast samples were subjected to the finish turning operation on a CNC horizontal lathe, using abundant amounts of cutting fluid emulsion containing 6% of water. The machining parameters employed here are listed in Table 02. The experiments were performed by varying the two machining parameters at two levels, in the following sequence: orthogonal rake angle of the insert ( $\gamma_o$ ) and cutting speed ( $v_c$ ), while the parameters depth of cut ( $a_p$ ) and feed rate ( $f$ ) were fixed. Interchangeable hard metal inserts were used with a coating composed of Ti(C,N) + Al<sub>2</sub>O<sub>3</sub> + TiN, in the ISO CNMG 120412 geometry, i.e., tool tip radius  $r_\epsilon=1.2$  mm, held in an ISO PCLNR 2525 M1 tool holder, with an angle tolerance ( $\alpha$ ) of 6° and a position angle ( $\chi_r$ ) of 95°.

Surface roughness was measured with a Perthometer M1–Mahr roughness tester, while residual stresses were measured with a RIGAKU D-MAX RINT 2200 X-ray diffractometer. All the hardness measurements were taken with a Buehler 1600-6300 microhardness tester, applying a load of 50 gf for 10 seconds.

### 3 – Results and Discussions

Table 02 lists the turning conditions applied and the respective values of roughness, Ra, residual tensile stress and surface hardening determined from the measurements of the machined surface.

Table 02 – Influence of turning conditions on the surface properties of CN3MN stainless steel.

Turning conditions				Roughness Ra ( $\mu\text{m}$ )	Residual stress (MPa)	Work hardening	
V <sub>c</sub> (m/min)	f (mm/v)	a <sub>p</sub> (mm)	$\gamma_o$ (°)			Surface hardness (HV <sub>50gf</sub> )	Thickness of layer ( $\mu\text{m}$ )
60	0.25	2.5	10	1.22	128 ± 15	464	165
90	0.25	2.5	10	1.31	179 ± 16	440	215
60	0.25	2.5	0	2.28	223 ± 30	471	215
90	0.25	2.5	0	2.10	339 ± 41	445	265

#### 3.1 – Roughness

As can be seen from the results in Table 01, the variable cutting speed had a significant effect on the roughness, Ra. The graph in Figure 01 illustrates the effects of the cutting parameters applied in turning on the roughness, Ra.

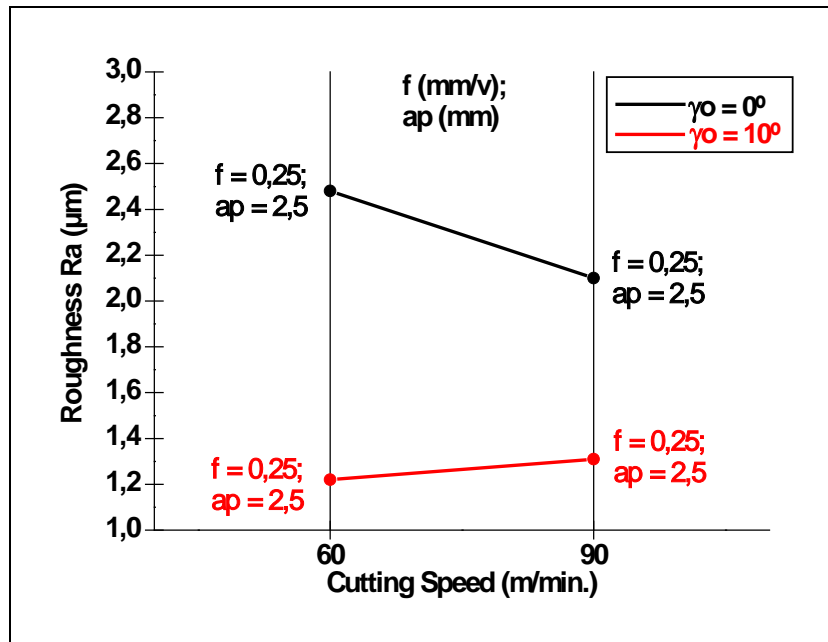


Figure 01 – Effect of cutting speed and rake angles on roughness Ra, for  $a_p = 2.5$  mm and  $f = 0.25$  mm/rot.

In Figure 01, note that the cutting speed does not influence roughness to any appreciable extent, but roughness decreases significantly when the rake angle of the insert ( $\gamma_o$ ) passes from  $0^\circ$  to  $10^\circ$ . This strong influence of the  $\gamma_o$  on roughness, Ra, indicates the high ductility of this machined material. With an increasing  $\gamma_o$ , the chip deformation rate decreases due to the decline in the decreasing specific cutting force ( $K_s$ ).

### 3.2 – Surface hardening

The graph in Figure 02 shows the microhardness profiles of the rough-machine samples, as well as an image representing the flat surface on which the microhardness measurements were taken.

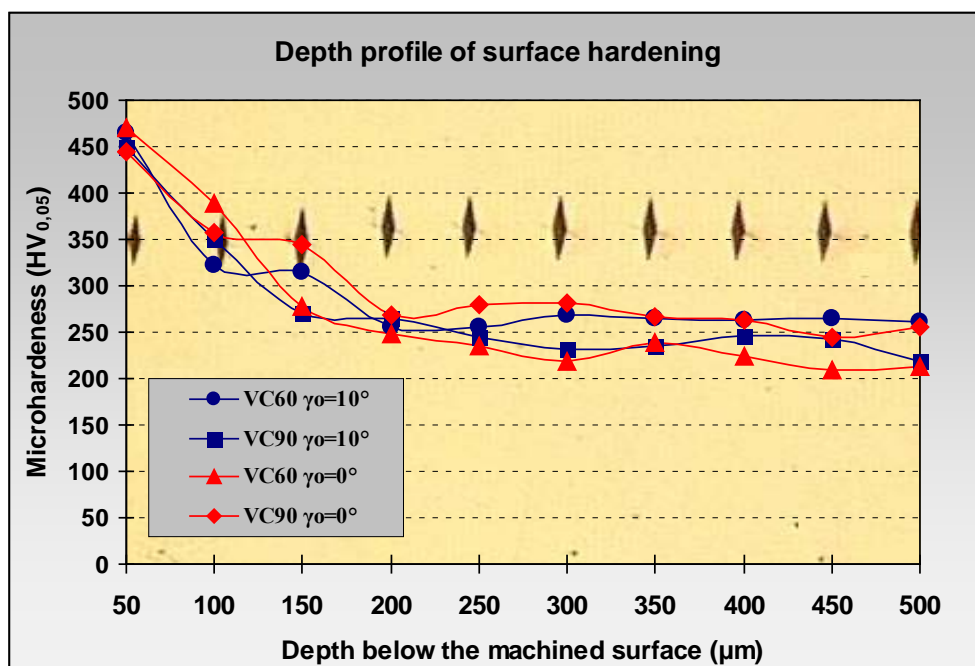


Figure 02 – Microhardness profiles of the 4 samples from the roughing operation.

Figure 02 shows the spacing of the notched markings that were produced by the Knoop hardness tester. The measurements were taken on the surface in the direction of the core up to a region where the hardness value approaches that of the core. As can be seen, the rough machining did not affect the material after passing a depth of 200  $\mu\text{m}$  from the machined surface. This high surface hardness can be attributed to the phenomenon of surface hardening.

The results of Table 02 indicate that all the turning conditions applied led to a high surface hardness when compared to the core hardness. The mean surface hardness was  $455 \pm 15$  HV. The thickness of the hardened layer varied from 165 to 265  $\mu\text{m}$ , with lower values of thickness obtained with the rake angle of  $10^\circ$  and cutting speed of 60 m/min. The graph in Figure 03 shows the effect of the variables used in the roughing operation on the microhardness value obtained in the samples.

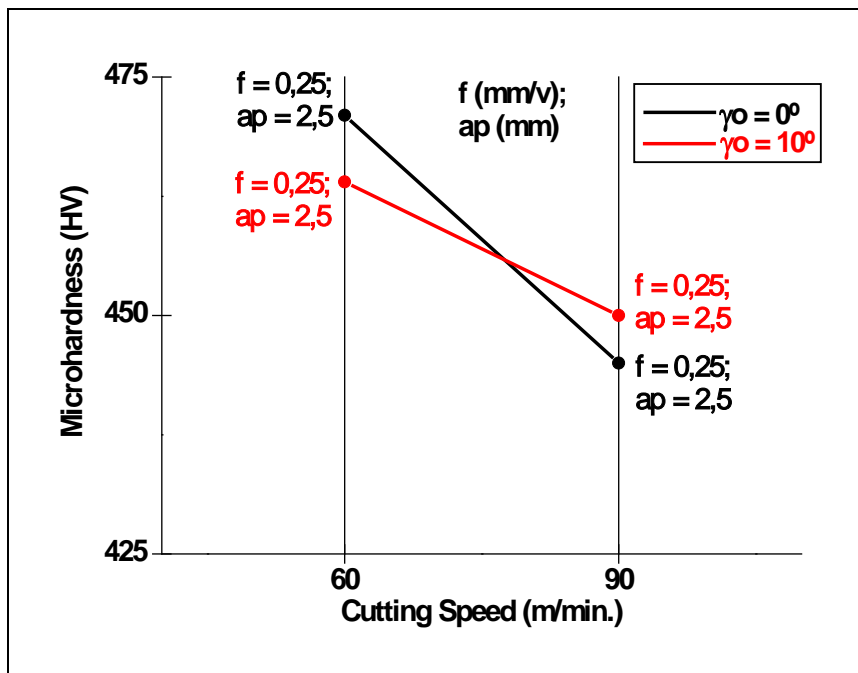


Figure 03– Effect of cutting speed and rake angles on surface hardness at  $a_p = 2,5$  mm and  $f = 0,25$  mm/rot.

It was found that increasing the cutting speed from 60 to 90 m/min contributed slightly to the surface hardness, causing a reduction in the order of 25 points on the Vickers scale. The rake angle of the insert had practically no effect on microhardness.

### 3.3 – Residual stress

Table 2 lists the residual stresses of the samples subjected to the roughing operation, which are positive (+), indicating residual tensile stress. The increase in residual tensile stress reduces the fatigue strength (Cullity et al., 2001). Tensile corrosion resistance is correlated with residual stress. The lower the values of residual tensile strength the lower is the possibility of cracking (Braham et al., 2005). The graph in Figure 04 illustrates the effect of the variables used in the roughing operation on the residual stress obtained in the samples.

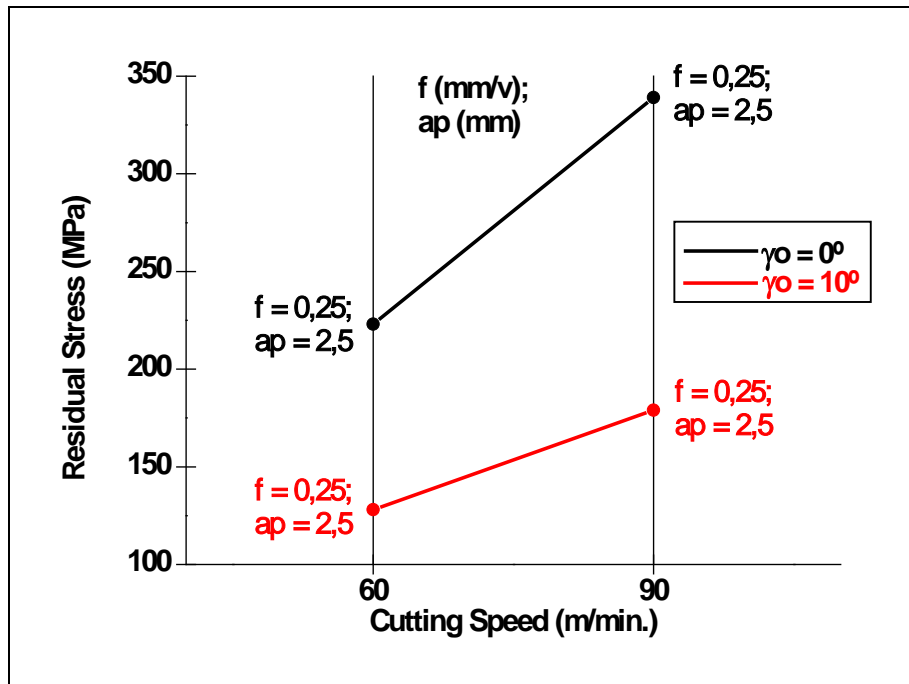


Figure 04 – Effect of cutting speed and rake angles on residual stress at  $a_p = 2.5$  mm and  $f = 0.25$  mm/rot.

Figure 04 indicates that increasing the tool rake angle to  $10^\circ$  and decreasing the cutting speed to 60 m/min the residual stress is reduced.

### 3.4 – Correlation between the input variables and the results obtained

Table 03 classifies the effect of the variables applied during machining on each of the three parameters of surface quality analyzed, according to the criterion of importance described below.

1 – Low roughness  $R_a$ . There is a correlation between pitting density per unit area and roughness,  $R_a$ . The lower the  $R_a$  the higher is the pitting corrosion resistance (Salina-Bravo et al., 1994; Ramanathan, 1998; Tuthil ET al., 1992).

2 – Low residual stress. With regard to residual tensile stress, the lower the value the higher the fatigue strength and the tensile corrosion resistance, even if the value does not reach the tensile yield point of the material (Cullity et al., 2001). In the study of tensile corrosion resistance of 316L austenitic stainless steel, no cracks appeared at the lowest values of residual tensile stress (Braham et al., 2005).

3 – Low microhardness. It was found that all the variables applied during machining led to surface hardening. The hardness, which ranged from 357 to 445 HV, indicates that all the samples underwent severe surface hardening when compared to the hardness of 211 HV of the core. Hardening is a characteristic that reduces the tool's life during machining, impairing machinability. The techniques for minimizing hardening include reducing chip deformation (higher  $V_C$ ,  $f$  and  $\gamma_o$ ) (Shaw, 2005; Trent et al., 2000; Diniz et al., 2003).

Table 03 – Effect of the variables on the surface quality.

Surface integrity in the roughing operation	Roughness, Ra	Hardened surface layer	Residual stress
↑ Cutting speed ( $V_c$ )	↕	↓	↑
↑ Rake angle – $\gamma_o$ ( $^\circ$ )	↘↘	↕	↘↘
↘ Lower – minor effect	↘↘ Lower – strong effect		
↑ Higher – minor effect	↑↑ Higher – strong effect	↕ Neutral effect	

From Table 03 it can be seen that to reduce the residual stress and roughness after rough machining requires increasing the tool's rake angle. To reduce surface hardness requires decreasing the cutting speed. Hence, the combination of variables recommended for rough machining is:  $v_c = 60$  m/min. and  $\gamma_o = 10^\circ$ .

## Conclusions

For the ASTM A744 Gr. CN3MN superaustenitic stainless steel subjected to rough turning machining applying the parameters of: feed-forward ( $f$ ) of 0.25 mm/rot., cutting depth ( $a_p$ ) of 2.5 mm, cutting speed ( $v_c$ ) of 60 and 90 m/min, and rake angle of the insert ( $\gamma_o$ ) of 0 and  $10^\circ$ , it was concluded that:

- Increasing the tool's rake angle from  $0^\circ$  to  $10^\circ$  resulted in a marked decrease in roughness, Ra, and residual stress, but had no effect on surface hardness.
- Increasing the cutting speed from 60 to 90 m/min led to a minor reduction in surface hardness and a slight increase in residual stress. The variation in cutting speed did not affect roughness, Ra.
- Among the variables applied in this study, the combination recommended to improve the surface integrity is the lowest cutting speed ( $v_c = 60$  m/min.) and the highest rake angle ( $\gamma_o = 10^\circ$ ).

## References

- American Society for Testing and Materials ASTM A743/A743M-06. *Standard Specification for Castings, Iron-Chromium, Iron-Chromium-Nickel, Corrosion Resistant, for General Application*, U.S.A, 2006, p. 7.
- BRAMAM, C.; BEN RHOUMA, A.; LÉDION, J.; SIDHOM, H., Effect of machining Conditions on Residual Stress Corrosion Cracking of 316L SS, *Materials Science Forum*, Vols. 490-491, Switzerland, 2005, pp. 305-310.
- CULLITY, B. D.; STOCK, S. R., *Elements of x-ray diffraction*, 3rd edition, Prentice Hall, U.S.A., 2001, pp. 435-466.
- CURTIS, J. F.; KOVACH, W., High Performance Stainless Steels. Nickel Development Institute, Pittsburgh, U.S.A., 2002, 95 p.
- DINIZ, A. E.; MARCONDES, F. C.; COPPINI, N. L., *Tecnologia da Usinagem dos Metais*, 4ª ed., Editora Artliber, São Paulo, 2003, p. 248.
- JANG, D. Y.; WATKINS, T. R.; KOZACZEK, K. J.; HUBBARD, C. R.; CAVIN, O. B., Surface residual stresses in machined austenitic stainless steel, *Wear*, 1996, vol. 194, pp. 168-173.
- MATSUMOTO, Y; BARASH, M. M.; LIU, C. R., Effect of hardness on the surface integrity of AISI 4340 steel, *Journal of Engineering for Industry*, 1986, vol. 108, pp.169-175.
- HASSIOTIS, N. D.; PETROPOULOS, G. P., Influence of surface roughness on corrosion resistance of turned carbon steel parts, *International Journal of Machining and Machinability of Materials*, 2006, vol. 1, n° 2, pp. 202- 212.
- MOAYED, M. H.; LAYCOCK, N. J.; NEWMAN, R. C., Dependence of the Critical Pitting Temperature on surface roughness, *Corrosion Science*, 2003, vol. 45, n° 6, pp. 1203-1216.
- RHOUMA, A. B.; BRAHAM C.; FITZPATRICK, M.E.; J. LÉDION, J.; SIDHOM, H., Effects of Surface Preparation on Pitting Resistance, Residual Stress and Stress Corrosion Cracking in Austenitic Stainless Steels, *Journal of Materials Engineering. Perf.*, 2001, pp. 507-514.
- RAMANATHAN, L. V., *Corrosão e seu controle*, 1ª ed., Hemus Editora Ltda, São Paulo, Brasil, 1998, p. 339.
- SHAW, M. C., *Metal cutting principles*, 2ª ed., Oxford University Press, New York, 2005, p. 432.
- SALINA-BRAVO, V. M.; NEWMAN, R. C., An Alternative Method to Determine Critical Pitting Temperature of Stainless Steels in Ferric Chloride Solution, *Corrosion Science*, 1994, vol. 36, n°1, pp. 66-77.
- TRENT, E. M.; WRIGHT, P. K., *Metal Cutting*, 2ª ed., Butterworth-Heinemann, Woburn, USA, 2000, p. 446.
- TUTHILL, A. H. OG AVERY, R. E., *Specifying Stainless Steel Surface Treatment*, NiDI Technical, Series n° 10.068, 1992.