

EFFECTS OF LOW TEMPERATURE AGING ON THE MECHANICAL PROPERTIES AND CORROSION RESISTANCE OF DUPLEX AND LEAN DUPLEX STAINLESS STEELS UNS S32205 AND UNS S32304

EFEITOS DE ENVELHECIMENTOS EM BAIXAS TEMPERATURAS NAS PROPRIEDADES MECÂNICAS E RESISTÊNCIA À CORROSÃO DOS AÇOS DUPLEX E “LEAN” DUPLEX UNS S32205 E UNS S32304

¹Francis Gabriel Wasserman, ¹Débora Carneiro Moreira, ¹Sergio Souto Maior Tavares, ¹Juan Manuel Pardal, ²Ricardo Augusto Faria & ³Cristiana dos Santos Nunes

¹Universidade Federal Fluminense, Departamento de Engenharia Mecânica/PGMEC, Rua Passo da Pátria, 156, Bloco D, S/302, CEP 24210-240 - São Domingos, Niterói-RJ; ²Arcelor Mittal Inox do Brasil - Centro de Pesquisa, Praça Primeiro de Maio, 9, Centro Timóteo MG; ³Universidade Federal do Ceará, Departamento de Engenharia Metalúrgica e de Materiais.

Abstract

Duplex stainless steels (DSS) with austenite-ferrite microstructure are high strength and corrosion resistant steels frequently used as pipes and accessories in chemical and petrochemical (on and off-shore) industries. Low temperature heat treatments (400–475 °C) may increase the hardness and wear resistance of duplex steels due to a spinodal decomposition reaction of the ferrite, whose small particles of Cr-rich α' precipitate in the matrix. In this work, several heat treatments at 400 °C and 475 °C with short duration (<24h) were performed in UNS S32304 and UNS S32205 grades. The kinetics of α' precipitation was studied by hardness measurements. The results of the two materials studied were analyzed and compared to each other. Tensile tests were also carried out for some heat treatment conditions to evaluate the effect of the aging on the ductility of both grades. The hardening of duplex UNS S32205 was more intense than UNS S32304, although both steels have shown interesting increase of tensile strength. Specimens of duplex steel heat treated at 475 °C for 4 h and 8 did not show any detectable decrease of corrosion resistance in anodic polarization and critical pitting temperature tests carried out in NaCl media.

Key words: duplex stainless steels, aging, mechanical properties.

Resumo

Os aços inoxidáveis duplex (AID) com microestrutura austeno-ferrítica são aços de alta resistência mecânica frequentemente utilizados em tubos e componentes nas indústrias química e petroquímica (“on” e “off-shore”). Tratamentos térmicos em baixas temperaturas (400-475 °C) podem aumentar a dureza e resistência ao desgaste devido a reação de decomposição espinoidal da ferrita, quanto finas partículas do precipitado α' rico em Cr se precipitam na matriz. Neste trabalho, diversos tratamentos térmicos de curta duração a 400°C e 475°C foram realizados nos aços UNS S32304 e UNS S32205. A cinética de precipitação foi estudada por meio de medidas de dureza. Os resultados dos dois materiais estudados foram analisados e comparados com outros graus de aços de estrutura austeno-ferrítica. Ensaio de tração foram realizados em algumas condições para se avaliar o efeito do envelhecimento na ductilidade dos dois aços. O endurecimento do aço UNS S32205 (“duplex”) é mais pronunciado do que o do aço UNS S32304 (“lean duplex”, ou “duplex baixa liga”), embora ambos os aços apresentem um ganho considerável de resistência com tratamentos térmicos de curta duração. Amostras de aço duplex tratadas a 475 °C por 4 h e 8 h não apresentaram qualquer prejuízo na resistência à corrosão nos ensaios de polarização cíclica e temperatura crítica de pites em meio contendo NaCl.

Palavras chave: aços inoxidáveis duplex, envelhecimento, propriedades mecânicas.

Introduction

Austenitic-ferritic stainless steels present excellent combination of corrosion resistance and mechanical properties in critical operation conditions. The higher mechanical and corrosion resistance is responsible for the increasing substitution of traditional austenitic grades by austenitic-ferritic grades.

The steels with austenitic-ferritic microstructure may be divided into *lean duplex*, *duplex*, *superduplex*, and, more recently, *hyperduplex* (Tavares et al., 2010).

The steels with low Mo content (<0.60%) are called lean duplex. Typical lean duplex steels have corrosion resistance comparable to traditional the most popular austenitic grades (AISI 316L and AISI 317L), but with superior yield limit and ultimate strength. The increase of Cr and N, and the addition of Mo in the chemical composition created the more corrosion resistant duplex and superduplex steels. The parameter used to distinguish these two sub-groups is the pitting resistance equivalent (PRE), which gives an indication of the pitting corrosion resistance of corrosion resistant alloys (CRA). The most used formulae for this parameter are the PRE_N and PRE_W (ASM, 1994):

$$\text{PRE ou PRE}_N = \%Cr + 3,3(\%Mo) + 16(\%N) \quad (1)$$

$$\text{PRE}_W = \%Cr + 3,3(\%Mo + \%W) + 16(\%N) \quad (2)$$

Austenitic-ferritic steels with PRE > 40 are called “superduplex”. The elements Cr, Mo and N are the most important for pitting corrosion resistance. Tungsten is also mentioned in equation (2), and is used in some superduplex steels. Recently, hyperduplex steels with PRE near 50 have been developed. These steels contain high contents of Cr, Mo and N, and also Ni, which is added to maintain the ferrite/austenite ideal proportion.

The increase of alloying elements addition from lean duplex to hyperduplex also increases the mechanical resistance and the cost of the material.

It is important to note that the PRE number is only a reference parameter. For instance, superduplex and hyperduplex steels may present very poor pitting corrosion resistance if undesirable phase transformations take place during manufacturing process (Gunn, 2003; Linton et al., 2004; Hitchcock et al., 2001). Intermetallic compounds (sigma and chi), chromium nitride (Cr₂N), and α' chromium rich precipitates are all prejudicial to corrosion resistance (Nilsson, 1992).

One of the most studied phase transformations in ferritic-austenitic steels is the spinoidal decomposition of ferrite into fine α' chromium rich precipitates and a Cr-depleted matrix (δ → α' + α''). This reaction occurs in the 350-550 °C range, and is faster at 475°C. As the prolonged aging causes hardening and decrease of toughness, this phenomena is often referred as 475°C embrittlement. The α' precipitates can only be directly observed by transmission electron microscopy, as shown in some previous works (Otárola et al., 2005; Solomon et al., 1979; Padilha et al., 2004). The α' precipitation have also been studied by other indirect methods, such as electrochemical tests (Yi et al., 1996), hardness tests (Tavares et al., 2000), Mossbauer spectroscopy (Lemoine et al., 1998; Solomon et al., 1978), and magnetic measurements (Tavares et al., 2000; Maeda et al., 1997; Isobe et al., 1996). The decrease of corrosion resistance due to prolonged aging in the 350-550°C range was investigated by double loop electrochemical potentiodynamic reactivation tests (DL-EPR), and with the proper choice of the test solution, an increase of the degree of sensitization with aging time could be observed (Tavares et al., 2005).

In this work the use of α' precipitation as hardening mechanism for lean duplex UNS S32304 and duplex UNS S32205 steels was studied. Short duration heat treatments at 400°C and 475°C were performed to evaluate the benefits and prejudicial effects.

Materials and Methods

The UNS S32304 and UNS S32205 steels studied were purchased as sheets of 1.8 mm of thickness, both in the annealed condition. Chemical compositions are presented in table 1.

Table 1: Chemical composition of UNS S32304 and UNS S32205 studied.

Grade	Cr	Ni	Mo	Mn	Si	N	Cu	C	P	S
UNS S32304	23	4,50	0,30	1,0	0,50	0,100	0,30	0,030	0,04	0,04
UNS S32205	22,5	5,30	2,90	1,85	0,32	0,166	0,03	0,023	0,03	0,001

The annealing of this class of material is a type of solution treatment in which the material must be soaked at 1000-1050°C and rapidly cooled to avoid deleterious phases precipitation on cooling. Light optical microscopy (LOM) was used to determine ferrite and austenite percentages, and also to investigate about the presence of deleterious tertiary phases. For austenite/ferrite quantification the specimens were prepared with Behara's etching (80ml H₂O + 20ml HCl + 0,3g potassium metabisulfite), and the analysis was performed by image analysis using Image Tool software (UTHSCSA, 2002). For deleterious phases investigation 5-10% KOH electrolytic etching (3V, 15 s) was used.

Specimens with 12 x 12 mm were cut and heat treated at 400°C and 475°C for 2, 4, 6, 8, 10, 12, 14, 16, 18 and 20 hours. These specimens were used to Vickers hardness tests with load of 30 kgf.

For some heat treatment conditions uniaxial tensile tests were performed to evaluate the variation of mechanical properties in tension. The specimens for uniaxial tension tests were cut and machined according to ASTM E370 standard (ASTM, 2009), with initial length (l_0) equal 75 mm. The tests were carried out at room temperature with velocity 12 mm/minute.

Three types of corrosion tests were also carried for some heat treatment conditions. Double loop electrochemical potentiodynamic tests (DL-EPR) are used to detect and quantify the sensitization of stainless steels (Cihal et al., 2001). In this work the tests for lean duplex and duplex steels were carried out at ambient temperature, using a potentiostat-galvanostat micro-AUTOLAB. For lean duplex the test solution was 2M H₂SO₄ + 0.01KSCN, and for duplex steel the test solution was 2M H₂SO₄ + 0.5M NaCl + 0.01M KSCN.

The DL-EPR tests were conducted in a conventional three-electrode cell using a Pt foil as the auxiliary electrode and a saturated calomel electrode (SCE) as the reference one. The working electrode was constructed using the lean duplex or duplex specimens embedded in epoxy resin, ground with 400 emery paper, degreased with alcohol and cleaned in water. The tests were initiated after nearly steady-state open circuit potential (E_{oc}) had been achieved, followed by the potential sweep in the anodic direction at 1 mV.s⁻¹ up to the potential of 0.3 V_{SCE} was reached. The scan was then reversed to the cathodic direction until the E_{oc} . The loss of corrosion resistance due to the chromium-depleted regions, i.e. the degree of sensitization (DOS), was evaluated from the ratio I_r/I_a , where I_a is the activation peak current of the anodic scan and I_r is the reactivation peak current in the reversed scan.

The two other corrosion tests were the cyclic polarization test and the critical pitting temperature (CPT) measurement. These tests were carried out only in some heat treatment conditions for duplex stainless steel UNS S32205.

Cyclic polarization tests were carried out at 40°C in 3.5% NaCl solution, according to ASTM G61 standard (ASTM, 1998). The CPT measurement was performed by the potentiostatic method. The potential was fixed in 0.700 V_{SCE} and the temperature was raised in a constant rate of 3°C/min. The CPT was the temperature correspondent to a current density of 100µA/cm². The method was similar to the ASTM G150 standard (ASTM, 2004), except for the higher heating rate applied in this work.

Results and discussion

Figures 1(a-b) show the microstructures of the materials in the as received condition. Lean duplex UNS S32304 has 63% of ferrite and duplex UNS S32205 has 65% of ferrite. Deleterious phases such as chi (χ) and sigma (σ) were not detected with KOH electrolytic etching (not shown).

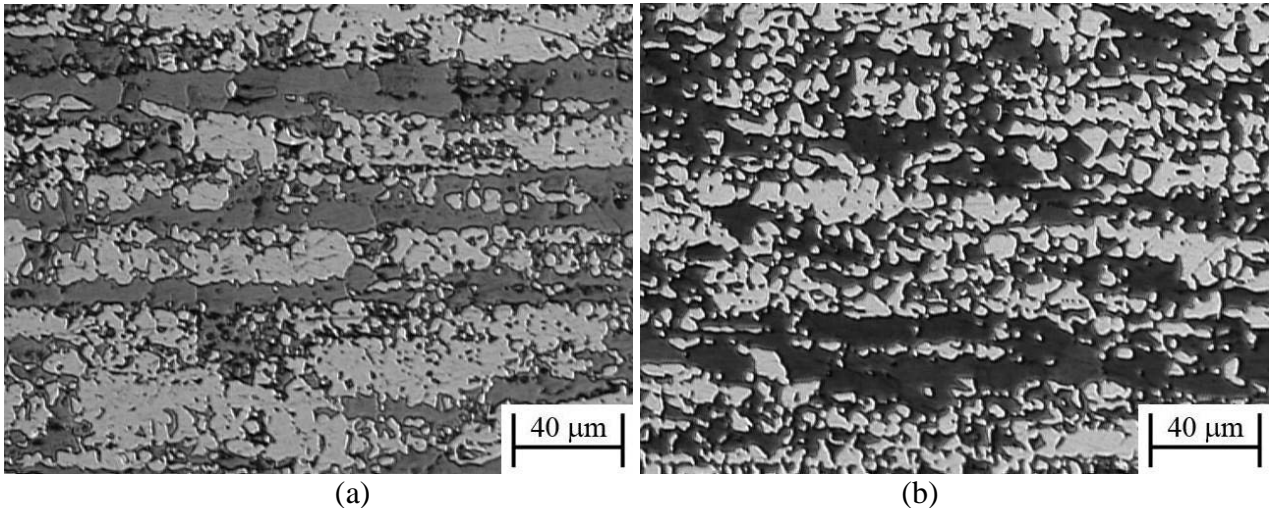


Figure 1: Microstructures of UNS S32304 (a) and UNS S32205 (b) steels in the as received condition.

Figures 2 and 3 show the hardness *versus* aging time curves at 475°C and 400°C for duplex UNS S32205 and lean duplex UNS S32304, respectively. Some important observations can be made in the light of these two figures. First, the aging at 475°C is more pronounced in both steels, as expected. In the first 10 hours of aging at 475°C the hardness of duplex steel was raised from 252HV to 313 HV ($\Delta HV = 61$ HV). In the lean duplex steel the variation of hardness in the same period and temperature is from 234 HV to 286 HV ($\Delta HV = 53$ HV). Figure 4 compares the hardness variation of duplex and lean duplex steels during aging at 475°C, where it is possible to note that the hardening is more intense in the duplex steel than in the lean duplex. This can be attributed to the higher Mo content of duplex, which enhances the kinetics of α' precipitation.

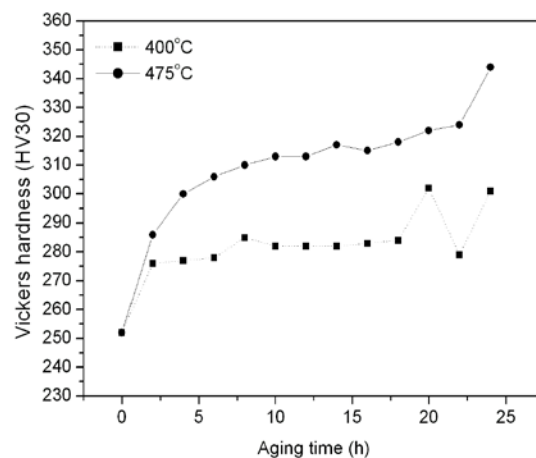


Figure 2: Hardness *versus* aging time curves for duplex UNS S32205 steel

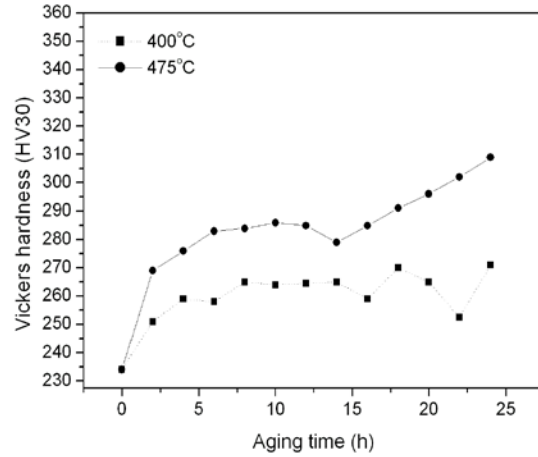


Figure 3: Hardness *versus* aging time curves for lean duplex UNS S32304 steel.

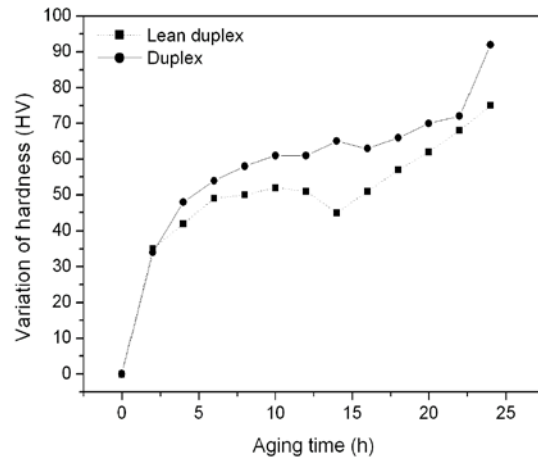


Figure 4: Variation of hardness during aging lean duplex UNS S32304 steel and duplex UNS S32205 steels.

The age hardening curves may be roughly divided into two parts. The initial stage is that of aging time up to 14 hours. At this initial stage the increase of hardening can be described by the equation 1:

$$HV_{(t)} = \frac{HV_i}{1 - a \cdot t^b} \quad (1)$$

where:

$HV_{(t)}$ – Hardness as function of time (HV)

HV_i – Initial value of hardness (HV)

a – constant

b – aging exponent

t – aging time (h)

Figures 5(a-b) show the curves adjusted for lean duplex and duplex aged at 475°C, respectively. Table 2 shows the values of a and b constants and correlation coefficients obtained.

Table 2: Constants of equation (1) adjusted for lean duplex UNS S32304 and UNS S32205 aged at 475°C.

Material	Constants of equation (1)			Correlation coefficients (R)
	HV_i	a	b	
UNS S32304	233	0,128899	0,132986	0.979
UNS S32205	252	0,110621	0,242834	0.995

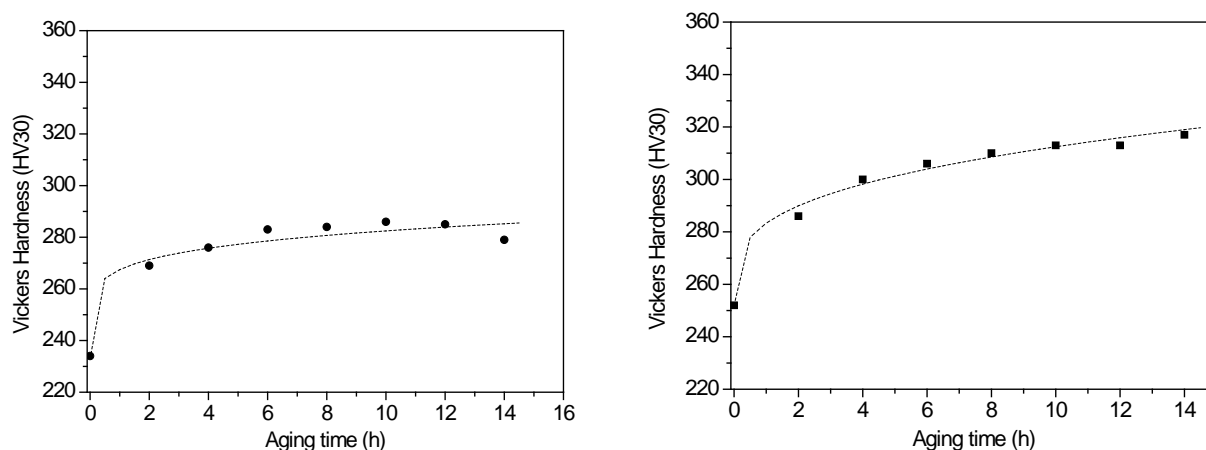


Figure 5: Curves fitted with equation (1) and parameters of table 2: (a) lean duplex; (b) duplex.

The interest in the initial stage of age hardening is the possibility to perform heat treatments able to hardens the material, with minimum prejudicial effects on corrosion resistance, ductility and toughness. In order to evaluate this possibility, two short duration heat treatments were chose for a more deep analysis by tensile and corrosion tests in both steel grades (duplex and lean duplex). The heat treatment chose were 475°C/4 hours and 475°C/8h. These heat treatments promote significant variation of hardness (ΔHV), as shown in figure 4.

Two tensile test specimens were produced per condition. Average values of yield limit (σ_{YL} , 0.2%), ultimate strength (σ_{UTS}), total elongation (El.), and nominal uniform ductility ($\epsilon_{unif.}$) are presented in table 3.

Table 3 also contains the values of toughness measured in the tensile tests. Toughness is commonly measured by impact tests, such as Charpy and Izod. However, as the sheets of duplex and lean duplex studied have thickness 1.88 mm, Charpy impact tests could not be done. The area under the curve tension-deformation curve gives a measure of the energy necessary to fracture per unit of area. Since the tests were conducted with the same experimental parameters (strain rate, temperature and specimens size), the toughness values obtained can be used to compare the different heat treatment applied.

Table 3: Tensile properties and hardness values for lean duplex steel UNS S32304 and duplex UNS S32205 in the heat treatment conditions indicated.

Properties	Lean duplex UNS S32304			Duplex UNS S32205		
	annealed	475°C/4h	475°C/8h	annealed	475°C/4h	475°C/8h
σ_{YL} , 0.2% (MPa)	534	632	660	573	676	706
σ_{UTS} (Mpa)	722	779	803	798	867	891
Hardness (HV)	234	276	284	252	300	310
El. (%)	29.7	27.1	23.9	28.2	24.2	23.5
$\epsilon_{unif.}$	22.2	18.5	17.0	21.1	18.6	18.4
Toughness (10^6 J/m ³)	216.0	209.8	203.4	205.5	195.3	182.0

The data exposed in table 3 show that a simple heat treatment at 475°C for 4 hours increase the yield limit of about 100 MPa in both steels. The ultimate strength increases 55 MPa in lean duplex and 69 MPa in duplex steel.

Table 4 shows the percentage variations of each tensile property based on the data of table 3. The spinodal decomposition of ferrite works as a typical hardening mechanism which decreases ductility and toughness. However, it seems that the choice for short duration heat treatments, may increase the mechanical resistance with a small decrease of toughness and ductility. It must be pointed that all fractures presented a typical ductile behaviour.

Table 4: Variations of tensile properties with the short duration treatments at 475°C.

Tensile Properties	Lean duplex UNS S32304		Duplex UNS S32205	
	475°C/4h	475°C/8h	475°C/4h	475°C/8h
$\sigma_{YL, 0.2\%}$	+ 18.4	+ 23.6	+ 18.0	+ 23.2
σ_{UTS}	+ 7.9	+ 11.2	+ 8.6	+ 11.7
Elongation	- 8.8	- 19.5	- 14.2	- 16.7
Toughness	- 2.9	- 5.8	- 5.0	- 11.4

Another important aspect to be evaluated is the effect of the heat treatments at 475°C for 4h and 8h on the corrosion resistance of steels. The corrosion tests were more concentrated on duplex steel, because lean duplex has a corrosion resistance significantly inferior to duplex, due to its lower PRE value.

Figure 6(a) shows the anodic polarization curve of UNS S32205 in the as received condition, i.e. with the annealing treatment. Figure 6(b) is from the same material aged at 475°C for 8 hours. Both curves were constructed at 40°C. The material aged at 475°C for 8 hours maintain high values of pitting and repassivation potentials, denoting that the critical pitting temperature is kept above 40°C after the treatment.

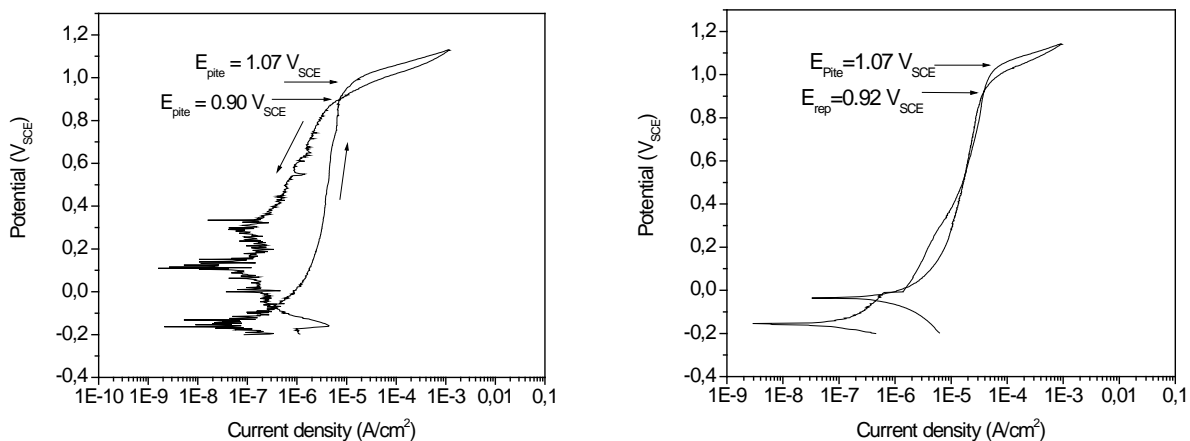


Figure 6: Cyclic polarization curves for duplex UNS S32205: (a) Annealed; (b) Treated at 475°C for 4 hours.

A second set of experiments was done specifically to determine the effect of the aging at 475°C on the critical pitting temperature (CPT) of duplex UNS S32205. Figures 7(a-c) show the potentiostatic curves for the determination of CPT in the specimens un-aged, aged at 475°C for 4 hours, and aged at 475°C for 8 hours, respectively. The CPT for the un-aged specimen is 52°C,

which is in accordance to other previous results (Gunn, 2003). The aging for 4 hours promotes a slight increase of CPT, which can be associated to diffusion of Cr, Mo and N in the material, eliminating local gradients of these elements. The specimen aged for 8 hours has $CPT = 53^{\circ}C$, which means that this aging time is not sufficient to decrease the pitting resistance of the material.

DL-EPR tests were applied in duplex and also lean-duplex steels. Figures 8(a-b) and 9(a-b) show the DL-EPR curves for duplex and lean duplex, un-aged and aged at $475^{\circ}C$ for 8 hours, respectively. Table 5 shows the I_r/I_a values obtained in each test. The results for duplex steel show that the aging for 8 hours was not sufficient to create Cr-depleted zones and provoke detectable sensitization. The results for lean duplex are quite different. The curve of the un-aged material presents a reactivation peak, which indicates that the test solution is still very aggressive to this class of material. The aging at $475^{\circ}C$ for 4 h and 8 h promotes a further increase of the I_r/I_a ratio, indicating that the material becomes sensitized with these treatments.



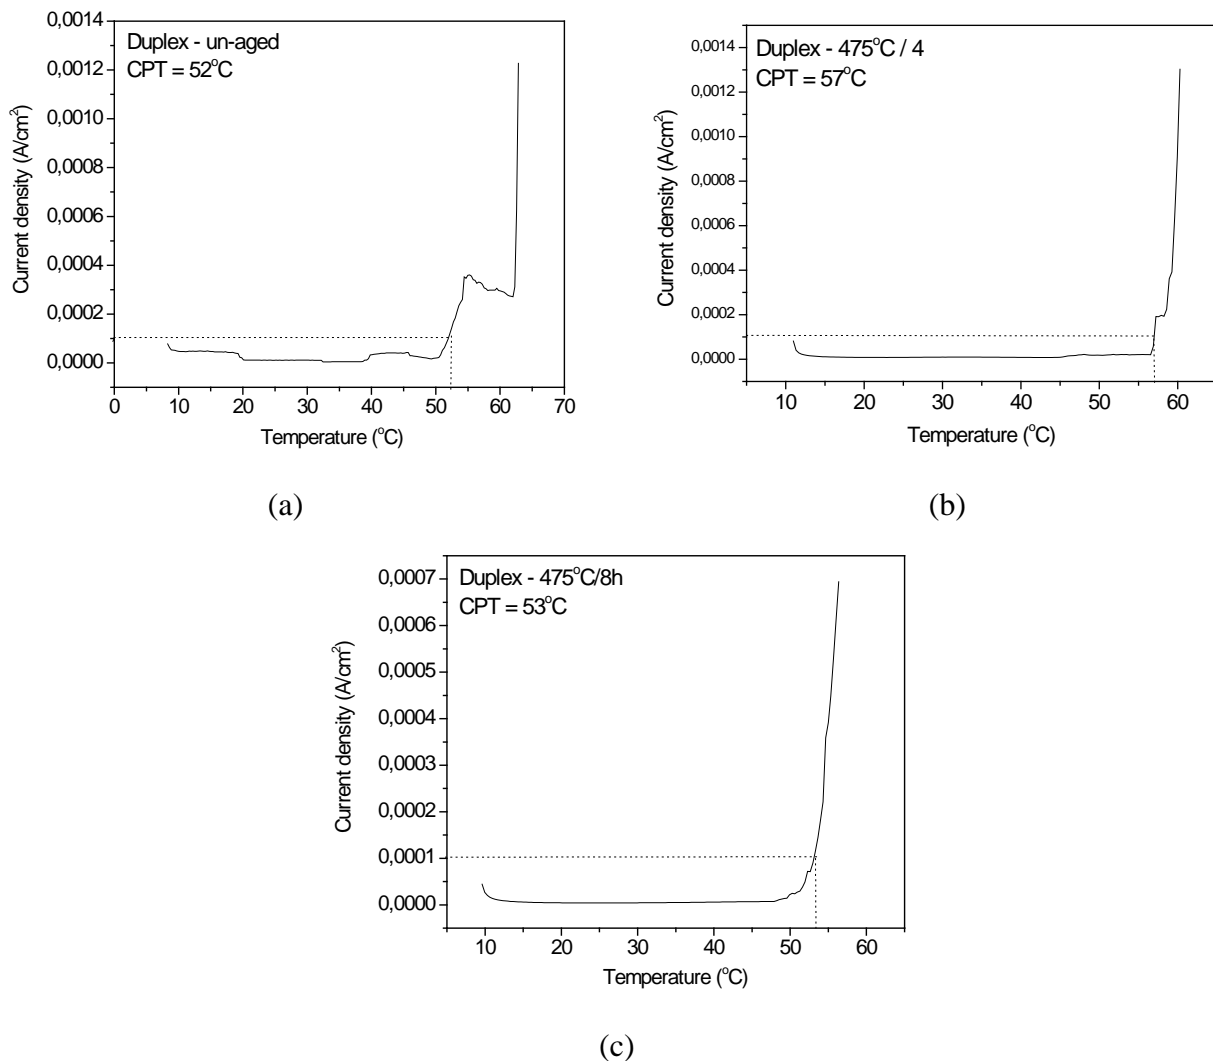


Figure 7: Density current x temperature curves for $E = 0.700V_{SCE}$ for determination of CPT in duplex UNS S32205: (a) Annealed; (b) Treated at $475^{\circ}C$ for 4 hours (c) Treated $475^{\circ}C$ for 8 hours.

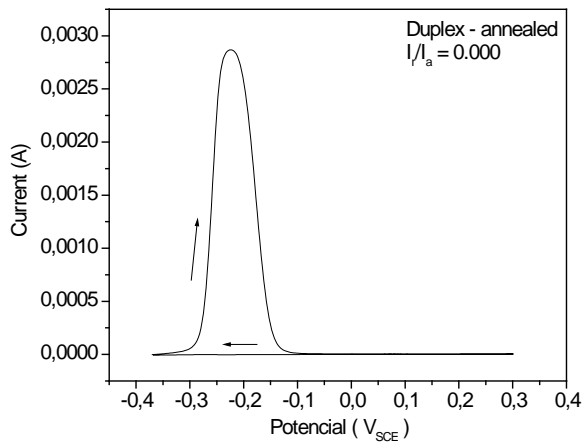


(a)

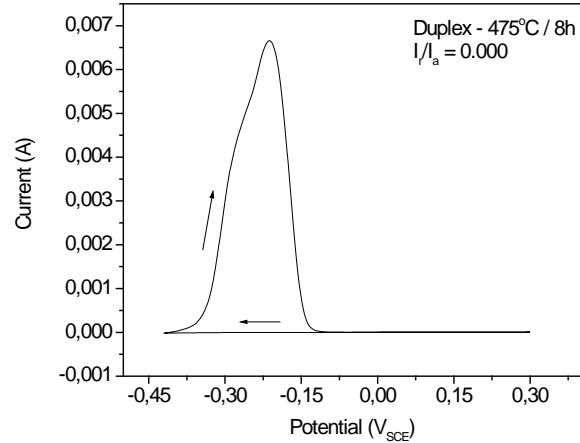


(b)

Figure 8: DL-EPR curves of duplex UNS S32205: (a) un-aged (annealed); (b) 475°C / 8 hours.

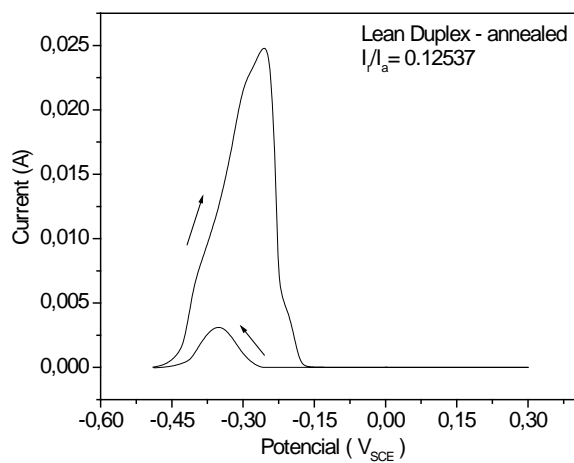

(a)

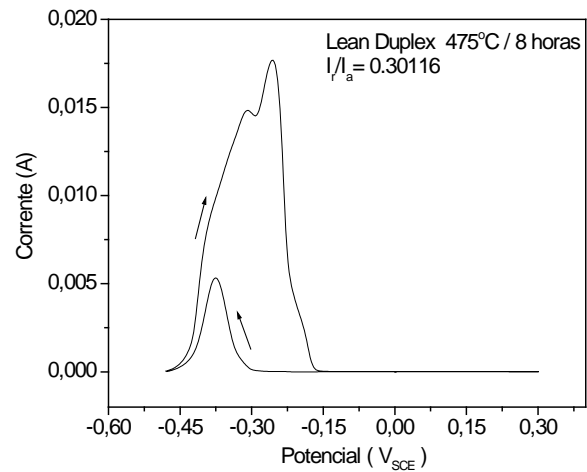

(b)

Figure 9: DL-EPR curves of lean duplex UNS S32205: (a) un-aged (annealed); (b) 475°C / 8 hours.

Table 5: I_r/I_a obtained from DL-EPR curves.

Material	annealed	475°C / 4 h	475°C / 8h
Lean duplex UNS S32304	0,125	0,280	0,301
Duplex UNS S32205	0,000	0,000	0,000

Conclusions

The results obtained in this work show that low temperature (475°C) and low duration (4h and 8h) heat treatments may be employed to increase the yield limit and ultimate strength of duplex and lean duplex steels with minimum effects on ductility and toughness. For instance, the heat treatment of duplex UNS S32205 steel at 475°C for 4 hours promoted an increase of 103 MPa in the yield limit and 69 MPa in the ultimate strength.

The aging at 475°C for 4 h and 8 h did not cause any detectable damage to corrosion properties of duplex UNS S32205 steel. Lean duplex, on the other hand, became more susceptible to sensitization according to DL-EPR tests.

Acknowledgements:

The authors acknowledge the Brazilian research agencies (CAPES, FAPERJ and CNPq) for financial support.

References

ASM Speciality Handbook Stainless Steels, American Society for Metals, Metals Park, OH 1994.

ASTM G61-98 – Standard Method for conducting cyclic potentiodynamic polarization measurements for localized corrosion susceptibility of iron-, nickel- or cobalt-based alloys, ASTM International, 1998.

ASTM G150-04 – Standard method for electrochemical critical pitting temperature testing of stainless steels, ASTM International, 2004.

ASTM E370-09 - Standard Test Methods and Definitions for Mechanical Testing of Steel Products, ASTM International, 2009.

ČIHAL, V., ŠTEFEC, R. On the development of the electrochemical potentiokinetic method, *Electrochim. Acta* 46 (2001) 3867-3877.

GUNN R.N. Duplex Stainless Steels-microstructure, properties and applications. Abbingdon Publishing, Cambridge, 2003, p. 203.

HITCHCOCK, G. R., DEANS, W. F., THOMPSON, D. S., COATS, A. Pin-hole and crack formation in a duplex stainless steel downhole tool, *Engineering Failures Analysis*, v.8, p.213-226, 2001.

ISOBE, Y, AOKI, K., NAKAYASU, F. Inspection of thermal aging of primary piping systems in nuclear power plants with squid magnetometer, *International Conference on Nuclear Engineering-ASME* 1996, v.5, 295-300, 1996.

LEMOINE, C., FNIDIKI, A., TEILLET, J., HÉDIN, M., DANOIX, F., Mössbauer study of the ferrite decomposition in unaged duplex stainless steels, *Scripta Materialia*, v.39, n° 1, p.61-66, 1998.

LINTON, V. M., LAYCOCK, N. J., THOMSEN, S. J., KUMPERS, A. Failure of a superduplex stainless steel vessel, *Engineering Failure Analysis*, v.11, p.243-256, 2004.

MAEDA, N., GOTO, T., KAMIMURA, T., NAITO, T., KUMANO, S., NAKAO, Y. Changes in electromagnetic properties during thermal aging of duplex stainless steel, *Int. Journal of Pressure Vessels & Piping*, v.71, p.7-12, 1997.

NILSSON, J.O. Super duplex stainless steels, *Materials Science and Technology*, v.8, p.685-700, 1992.

OTARÓLA, T., HOLLNER, S., BONNEFOIS, B., ANGLADA, M., COUDREUSE, L., MATEO, A. Embrittlement of a superduplex stainless steel in the range of 550-750°C, v.12, p.930-945, 2005.

PADILHA, A.F., GUEDES, L.C., Aços inoxidáveis austeníticos: microestrutura e propriedades, Ed. Hemus, 2004, p.170.

SOLOMON, H.D., LEVINSON, L.M. Mössbauer effect study of 475°C embrittlement of duplex and ferritic stainless steels, *Acta Metallurgica*, v. 26, p.429-442, 1978.

SOLOMON, H.D., KOCH, E.F., High temperature precipitation of α' in a multicomponent duplex stainless steel, *Scripta Metallurgica*, v.13, p.971-974, 1979.

TAVARES, S.S.M., da SILVA, M.R., NETO, J. M., Magnetic property changes during embrittlement of a duplex stainless steel, *Journal of Alloys and Compounds*, v.313, p.168-173, 2000.

TAVARES, S.S.M., TERRA, V.F., LIMA NETO, P., MATOS, D. Corrosion resistance evaluation of the UNS S31803 duplex stainless steels aged at low temperatures (350 to 550°C) using DL-EPR tests. *Journal of Materials Science*, v. 40, p.4025-4028, 2005.

TAVARES, S.S.M., PONZIO, E.A., PARDAL, J.M., LOUREIRO, A., SOUZA, J. A. Influence of microstructure on the corrosion resistance of hyperduplex stainless steel, *Materials and Corrosion*, v.61, nº 4, p.313-317, 2010.

UTHSCSA, Image Tool Version 3.0 Department of Dental Diagnostics Science at Texas Health Science Center (UTHSCSA), San Antonio, Texas, 2002. Available in the website <http://ddsdx.uthscsa.edu/dig/itdesc.html>

YI, Y.S., SHOJI, T. Detection and evaluation of material degradation of thermally aged duplex stainless steels: electrochemical polarization test and AFM surface analysis, *Journal of Nuclear Materials*, v.231, p.20-28, 1996.

Corresponding author: Sergio Souto Maior Tavares (ssmtavares@terra.com.br)